

RAPID COMMUNICATION

Open Access



Influence of soil properties on the heartwood colour of *Juglans mandshurica* var. *sachalinensis* in a cool temperate forest

Kobayashi Makoto^{1*†}, Elizaveta Susloparova^{2†}, Ikutaro Tsuyama³, Takuya Shimase³, Satoshi Nakaba⁴, Naoki Takahashi⁵ and Toshiya Yoshida⁶

Abstract

Heartwood colour is often an important factor in determining timber prices. However, the determinants of intraspecific variation in heartwood colour, which is useful information for sustainable wood marketing, are little understood, especially at the local scale in cool temperate forests. Because heartwood is produced as a secondary compound and photosynthesis is regulated by nitrogen (N) in cool temperate forests, we hypothesized that (1) soil conditions determine heartwood colour even at a local scale within a tree species and (2) N, specifically, can be an important driver of the intraspecific variation in heartwood colour in the trees of cool temperate forests. To test these hypotheses, we investigated the relationship between the colour values (luminescence, redness, and yellowness) of heartwood from *Juglans mandshurica* var. *sachalinensis* and the soil parameters in a cool temperate forest. Among the soil properties, not soil N but soil magnesium (Mg) contents alone had a significant influence on the redness and yellowness of the heartwood. Higher soil Mg contents resulted in increased greenness and yellowness of the heartwood in our study, probably due to the increase in phenolics and the colouring of the tannins in the heartwood with Mg. Our results indicate that even at a local scale, soil condition can determine the intraspecific variation in heartwood colour and that forest managers can utilize edaphic information to predict heartwood colour for timber marketing.

Keywords: Soil nutrients, Heartwood colour, Ecosystem service, Local timber production

Introduction

Wood colour is often an important factor in determining timber prices. Thus, understanding the determinants of wood colour is useful for effectively using ecosystem services and the sustainable marketing of wood [1, 2]. Species differences are well known to be determinants of wood colour. On the other hand, even within the same species, wood colour can differ

¹ Teshio Experimental Forest, Field Science Center for Northern Biosphere, Hokkaido University, Horonobe, Hokkaido 098-2943, Japan Full list of author information is available at the end of the article



^{[2],} making the economic value of the wood markedly different (e.g., the heartwood colour of birch in Japan, [3]). Previous studies have revealed that environmental factors such as soil properties are important in determining wood colour [2, 4]. For instance, in Costa Rican plantations across the country, the wood colour of *Tectona grandis* varies with soil type and coincidental difference of chemical properties; pH; and calcium (Ca), magnesium (Mg), and iron (Fe) contents [2]. For five tree species in Mali, soil type is an important factor, driving the intraspecific variation in wood colour (especially redness and yellowness) across the nation [4]. For *Juglans nigra* in the USA, the luminance of wood differs between two states due to differences

^{*}Correspondence: makoto@fsc.hokudai.ac.jp

[†]Kobayashi Makoto and Elizaveta Susloparova contributed equally to this manuscript

in soil properties [5]. The heartwood colour of *Cryptomeria japonica* differs depending on the soil moisture contents across a topographic region and the coincidental soil conditions [6]. However, there is a large knowledge gap about the determinants of heartwood colour in cold biomes, although forests in cold biomes are important for timber production [7]. In summary, little is known about the drivers of intraspecific variation in heartwood colour at a local scale in cold biomes, which makes it difficult for local forest managers to predict wood colour, information that is needed for marketing.

Heartwood substances are heartwood-specific secondary metabolites produced during tree growth [8]. Furthermore, tree growth in cold biomes, such as cool temperate forests, is known to be regulated by nitrogen (N) availability [9]. Based on these facts, we hypothesize that (1) soil condition drives the intraspecific variation in heartwood colour at a local scale (within a few kilometres) and (2) N, specifically, can be the determining factor of heartwood colour within a tree species in cool temperate forests. To test these hypotheses, we investigated the relationship between the colour index of the heartwood of Juglans mandshurica var. sachalinensis and the soil parameters in a cool temperate forest of northern Japan, which is the northern edge of the distribution of this species. J. mandshurica var. sachalinensis is one of the most economically valuable tree species in northern Japan; thus, understanding the determinants of the heartwood colour of this species would be helpful in the utilization and marketing of timber resources by local forest managers.

Methods/experimental

Study site

Wood samples from mature individuals of J. mandshurica var. sachalinensis were obtained in a natural mixed forest in Nakagawa town, northern Hokkaido, Japan. The understory was mainly covered by dwarf bamboo (Sasa sananensis (Fr. et Sav.) Rehder), which is the dominant species in northern Japan, and the thickness of the litter layer was about 2-3 cm. Between 1981 and 2010, the average mean annual air temperature of this area was 5.5 °C and the annual precipitation was 1225 mm (Japan Meteorological Agency 2020). To assess the importance of environmental gradients at a local scale (which is the important unite for the local forest manager), all the individuals were separated from each other by less than 3 km horizontally and 50 m vertically; therefore, the climate variables can be regarded as relatively homogeneous. The bedrock of the study site was terrace deposits from the late Holocene.

Sampling and wood colour measurements

A disc sample was obtained at a height of 30 cm from the bottom of the stem in each individual. In total, 17 mature individuals were sampled. The number of intraspecific individual replications was comparable to Montes et al. [4]. The average diameter at breast height (DBH) was 45 cm. The obtained samples were dried at 70 °C for 2 weeks. Although the drying process at 70 °C can change the wood colour from the original one, we employed this drying temperature because it is common to dry the wood at this temperature range for wood industry in Japan and one of our major aims of this study is the contribution to the better wood marketing. After drying, the surface of the flat-grained tangential face was carefully polished with sandpaper to prepare it for heartwood colour analysis. For each sample, three points were selected, and the heartwood colour was measured using a colour meter (ZE6000, Nihon Denshoku-kogyo, Japan) under stable temperature and humidity conditions. Before the measurements, calibration was conducted using a white standard reference supplied by the same company. The measurement was set within the visible range of 400-700 nm at intervals of 10 nm. According to HunterLab (1995), we estimated the heartwood wood colour in three coordinates: the L value (luminescence) represents the position on the black-white axis (L00 represents black; L0100 represents white), a value defines the position on the redgreen axis (+100 values indicate red; -100 values indicate green), and b value defines the position on the yellow-blue axis (+100 values indicate yellow; -100values indicate blue).

Soil measurements

From the areas surrounding each tree, three subsamples of soil (from a depth of 0-20 cm) were obtained; the three subsamples were merged to form a composite representative sample for each tree. The soil analysis was conducted following the methods presented by a previous study [10]. In short, by using the total wet weight of the samples and gravimetric water contents, the bulk density of the soil was calculated. To determine the pH, 10 g of soil was shaken with 25 mL of deionized water, and the solution was measured with a pH meter (B212, Horiba, Japan). The total N concentration was measured with a CHNS/O analyser (2400II, Perkin Elmer, USA). Following [5], the exchangeable nutrients (P, Ca, Mg, K, Fe, Al, Cu, Mn, Zn, and S) were extracted with 100 mL 1N ammonium acetate solution from 10 g fresh samples, and their contents in the extracts were determined by inductively coupled plasma spectroscopy (IRIS, Jarrel Ash, Franklin, MA). The concentrations of all the

nutrients and cations were determined on the basis of the soil dry mass.

Statistical analysis

The correlations between each of the colour values and each of the soil properties were analysed with a generalized linear model (GLM). The error distribution and the link function were set as Gaussian and log, respectively. The relationship between each of the wood colour values and the soil properties was regarded as significant when the p value was less than 0.05. The fit of the GLM was evaluated with the proportion of explained deviance of the model (D^2) [11]. All the statistical analyses were conducted with R 3.5.1 (R Core Team 2018).

Results and discussion

The soil Mg contents had a significant relationship with only the a value (redness) (Table 1, p < 0.01, $D^2 = -0.48$). High soil Mg contents resulted in more greenish heartwood in J. M mandshurica var. M sachalinensis (Fig. 1a). Furthermore, the M value was significantly correlated with the soil Mg content (Table 1, M value) when the soil Mg content was more yellowish when the soil Mg content was high (Fig. 1b). These results indicate, as we hypothesized, that the soil condition significantly influenced the heartwood colour of M mandshurica var. M sachalinensis, even at a local scale. On the other hand, the soil N contents were not correlated with the heartwood

Table 1 Statistical results about the relationship between soil chemical properties and heartwood colour values

	L	а	ь
Bulk density	N.S	N.S	N.S
Water contents	N.S	N.S	N.S
рН	N.S	N.S	N.S
Total C contents	N.S	N.S	N.S
Total N contents	N.S	N.S	N.S
Exchangeable P contents	N.S	N.S	N.S
Exchangeable Ca contents	N.S	N.S	N.S
Exchangeable Mg contents	N.S	-0.69**	0.64**
Exchangeable K contents	N.S	N.S	N.S
Exchangeable Fe contents	N.S	N.S	N.S
Exchangeable Al contents	N.S	N.S	N.S
Exchangeable Cu contents	N.S	N.S	N.S
Exchangeable Mn contents	N.S	N.S	N.S
Exchangeable Zn contents	N.S	N.S	N.S
Exchangeable S contents	N.S	N.S	N.S

L value is for luminescence that represents the position on the black—white axis, a value that defines the position on the red—green axis, and b value that defines the position of the yellow—blue axis (see the details in Material and Method section). The number in the table is D values calculated based on D^2 value by [3]. Asterisk (**) show the statistically significant relationship (p < 0.01) determined by GLM

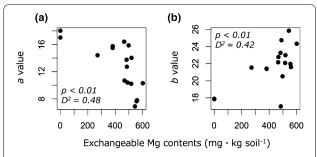


Fig. 1 Relationship between colour values (a and b) of *Juglans mandshurica* var. *sachalinensis* and exchangeable Mg contents in soil. The statistical significance of the relationship was shown as p value analysed with GLM. The fitness of the GLM was defined with D^2 value following [3]

colour of J. mandshurica var. sachalinensis, which is contrary to our hypothesis. Tree photosynthesis and coincidental productivity in cool temperate forests are known to be generally strongly regulated by N [9]. Our results indicated that rather than altering heartwood colour via the regulation of tree photosynthetic activity, which is related to growth, soil conditions alter heartwood colour via other physiological processes. The wood colour of Juglans species is related to the extractive contents and wood density [12]. The causes of intraspecific variation in wood colour are suggested to be driven by differences in the physiological processes of trees [13], although the specific physiological mechanism was not pointed out in their study. Furthermore, the soil physical properties are also known to influence the wood properties [14], which should be investigated in detail in future study.

In a Costa Rican plantation, intraspecific variation in the heartwood colour of T. grandis was driven by soil Mg contents [2]. In that study, together with other base cations, a high Mg content was regarded as a proxy of soil fertility in Ultisol, and fertility was suggested to change the heartwood colour. Similarly, soil Mg had a significant influence on wood colour of J. nigra [5]. These results, which were observed across a wide spatial scale, were consistent with our results, showing the importance of Mg in determining heartwood colour. In J. nigra and J. regia, ellagic acid derivatives, which are the components of hydrolysable tannins, are one of the major heartwood substances [1]. Similarly, gallic acid, ellagic acid and hydrolysable tannins have been found in heartwood in J. mandshurica var. sachalinensis [15, 16]. Mihara [17] reported that magnesium oxide reacts with tannin creating a different colour. Therefore, it is possible that Mg affect the heartwood colour of J. mandshurica var. sachalinensis by reacting with tannins. On the other hand, Mg is important for the various metabolic processes of trees [18]. Soil Mg contents function not Makoto et al. J Wood Sci 2021, 67(1):

only as photosynthetic pigments that are directly related to carbon fixation, but also as accelerators of phenolic accumulation. Li et al. [18] reported that Mg contents can change the activity of phenylalanine ammonia-lyase (PAL), which relates to the production of phenolic compounds, and that of polyphenol oxidase (PPO) and guaiacol peroxidase (GPX), which relates to the oxidization of phenolic compounds in roots. Phenolic compounds are one of the major components of heartwood substances [19] and are also known to influence the colour of heartwood of Juglans species [1]. In Acacia mangium and Vochysia guatemalensis, phenolic contents affect colour of wood [20]. Therefore, it is possible that Mg can change the phenol-related metabolism in the stems of trees (which is non-assimilatory organs such as roots), consequently changing the amount and composition of phenolic compounds in the heartwood of *J. mandshurica* var. sachalinensis. However, to the best of our knowledge, it is not known whether the increase of phenolic compounds directly result in then increase of colouring material or indirectly change the colour reaction in Juglans species, which should be clarified in the future study.

Because it takes time for Juglans trees to start producing heartwood, a long-term experiment in which Mg is added to soil may be necessary to understand the role of soil nutrients (in this case, Mg) in determining heartwood colour; in turn, this knowledge could be applied to control Juglans wood colour, supporting sustainable wood production. Notably, there was not a clear relationship between tree diameter and any of the wood colour parameters, which implicate that, among the matured trees, the edaphic condition influences the heartwood colour rather than the tree age (data not shown). In USA, the average rate of diameter growth and tree age of Juglans nigra did not correlate with any parameters of wood colour (luminance, dominant wavelength, and purity), while soil properties (specifically, soil pH, available P, exchangeable Mg, K, Ca, and total N) were correlated with the above-mentioned wood colour parameters [5]. In their study, the age of investigated individuals of Juglans nigra ranges from 48 to 122 years, which indicates that, together with our observation, the age of Juglans trees has little influence on wood colour among the matured individuals.

There were two points where the exchangeable Mg concentration was under detectable (Fig. 1). By considering that other soil macro-nutrients (Ca, K, Fe, Al) were detected in the same solutions from two points [21], the failure of the detection for exchangeable Mg in soil would be not due to the artefact during analysis but to the little solubility of Mg in the soils of these two points. Exchangeability of Mg in soil is strongly determined by the soil depth to the bedrock, slope position and acidity

in temperate forests [22]. In the future study, we should also clarify the determinant of exchangeable Mg in soil across the landscape.

The GLM revealed that none of the soil properties had a significant effect on the L value. In [5], the L (luminance) value of J. nigra differed between two regions in the USA. In their study, the combination of exchangeable Mg and available P predicted 30% of the variation in heartwood luminance. The contrasting effect of Mg and P on the L value between our study and the previous study might be partly due to the difference in context between the studies (e.g., spatial scale, difference in absolute amount of nutrients, and climate), even within the same genus. It is better to investigate the determinants of heartwood colour for economically valuable species at the local scale. Our results indicate that the local forest managers can utilize edaphic conditions (specifically soil Mg) to predict the heartwood colour of harvested walnut for efficient marketing in northern Japan.

Conclusion

The heartwood colour of *Juglans mandshurica var. sachalinensis* showed large variation according to soil properties. Our study demonstrated that soil Mg content could be an important factor in determining the variation of heartwood colour of this species at a local scale. Specifically, high soil Mg contents resulted in more reddish and more yellowish heartwood.

Acknowledgements

We sincerely thank Dr. A. Nakanishi for providing GPS data of the tree individuals and support during the field work. We also appreciate Mr. F. Endo and the staff of the town office of Nakagawa town for providing the research site and support the field work, Drs. M. Sato and S. Isaji for their support of wood colour measurement.

Authors' contributions

MK, TI, ST, TN, YT designed the research. MK, TI, ST, TN and YT conducted the wood sampling. ST and TI conducted the wood colour measurements. MK and SE conducted the soil sampling and the statistical analysis. MK led the writing of the manuscript. All authors contributed significantly for the improvement of the manuscript. All authors read and approved the final manuscript.

Funding

This research was partly supported by the fund provided by Human Resource Development Platform for Japan–Russia Economic Cooperation and Personnel Exchange (HaRP) project.

Availability of data and materials

The dataset used in this study is available at Dryad https://doi.org/10.5061/dryad.3bk3j9kjr

Declarations

Competing interests

The authors have no conflicts of interest directly relevant to the content of this article.

Author details

¹Teshio Experimental Forest, Field Science Center for Northern Biosphere, Hokkaido University, Horonobe, Hokkaido 098-2943, Japan. ²Institute of Geology

and Nature Management, Far Eastern Branch, Russian Academy of Sciences, Blagoveshchensk 675000, Russia. ³Hokkaido Research Center, Forestry and Forest Products Research Institute, 7 Hitsujigaoka, Toyohira-ku, Sapporo, Hokkaido 062-8516, Japan. ⁴Faculty of Agriculture, Tokyo University of Agriculture and Technology, 3-5-8 Saiwai-cho, Fuchu, Tokyo 183-8509, Japan. ⁵Division of Industrial Promotion, Town Office of Nakagawa Town, Nakagawa, Hokkaido 098-2802, Japan. ⁶Field Science Center for Northern Biosphere, Hokkaido University, Nayoro, Hokkaido 096-0071, Japan.

Received: 18 April 2021 Accepted: 8 July 2021 Published online: 19 July 2021

References

- Burtin P, Jay-Allemand C, Charpentier JP, Janin G (1998) Natural wood colouring process in *Juglans* sp. (*J. nigra*, *J. regia* and hybrid *J. nigra* 23 x *J. regia*) depends on native phenolic compounds accumulated in the transition zone between sapwood and heartwood. Trees Struct Funct 12:258–264. https://doi.org/10.1007/PL00009716
- Moya R, Calvo-Alvarado J (2012) Variation of wood color parameters of Tectona grandis and its relationship with physical environmental factors. Ann For Sci 69:947–959. https://doi.org/10.1007/s13595-012-0217-0
- Koike T (2013) Environment to produce valuable wood for five broadleaved tree species. Northern For 65:109–112 (in Japanese)
- Montes CS, Weber JC, Garcia RA, Silva AD, Muñiz GIB (2013) Variation in wood color among natural populations of five tree and shrub species in the Sahelian and Sudanian ecozones of Mali. Can J For Res 43:552–562. https://doi.org/10.1139/cjfr-2012-0510
- Nelson ND, Maeglin RR, Wahlgren HE (1969) Relationship of Black Walnut wood color to soil properties and site. Wood Fiber 1:29–37
- Kubo T, Ataka S (1998) Blackening of sugi (*Cryptomeria japonica* D. Don) heartwood in relation to metal content and moisture content. J Wood Sci 44:137–141. https://doi.org/10.1007/BF00526259
- Gauthier S, Bernier P, Kuuluvainen T, Shvidenko AZ, Schepaschenko DG (2015) Boreal forest health and global change. Science 349:819–822
- Celedon JM, Bohlmann J (2018) An extended model of heartwood secondary metabolism informed by functional genomics. Tree Physiol 38:311–319. https://doi.org/10.1093/treephys/tpx070
- LeBauer DS, Treseder KK (2008) Nitrogen limitation of net primary productivity in terrestrial ecosystems is globally distributed. Ecology 89:371–379. https://doi.org/10.1890/06-2057.1
- Makoto K, Shibata H, Kim YS, Satomura T, Takagi K, Nomura M, Satoh F, Koike T (2012) Contribution of charcoal to short-term nutrient

- dynamics after surface fire in the humus layer of a dwarf bamboodominated forest. Biol Fertil Soils 48:569–577. https://doi.org/10.1007/s00374-011-0657-v
- 11. Guisan A, Weiss SB, Weiss AD (1999) GLM versus CCA spatial modeling of plant species distribution. Plant Ecol 143:107–122
- Hiller CH, Freese F, Smith DM (1971) Relationships in black walnut heartwood between color and other physical and anatomical characteristics. Wood Fiber Sci 4:38–42
- 13. Sullivan JD (1967) Color characterization of wood: color parameters of individual species. For Prod J 17:25–29
- Moya R, Perez D (2008) Effects of physical and chemical soil properties on physical wood characteristics of *Tectona grandis* plantations in Costa Rica. J Trop For Sci 20:248–257
- Kondo T, Ito T, Suda M (1956) On the heartwood components of *Juglans sieboldiana* Maxim. Mokuzai Gakkaishi 2:221–222 (in Japanese with English summary)
- Kishimoto J, Fukuta T, Sakuno T, Furukawa I (1981) Studies on the chemical identification of wood (II). Bull Faculty Agric Tottori Univ 33:65–69 (in Japanese with English summary)
- Mihara K (1964) Tannin for anticorrosion agent. J Jpn Soc Colour Mater 37:62–67. https://doi.org/10.4011/shikizai1937.37.62
- Li CP, Qi YP, Zhang J, Tang LT, Wang DH, Ye X, Lai NW, Tan LL, Lin D, Chen LS (2017) Magnesium-deficiency-induced alterations of gas exchange, major metabolites and key enzymes differ among roots, and lower and upper leaves of *Citrus sinensis* seedlings. Tree Physiol 37:1564–1581. https://doi.org/10.1093/treephys/tpx067
- Miranda I, Sousa V, Ferreira J, Pereira H (2017) Chemical characterization and extractives composition of heartwood and sapwood from *Quercus faginea*. PLoS ONE 12:1–14. https://doi.org/10.1371/journal.pone.017926
- Moya R, Fallas RS, Bonilla PJ, Tenorio C (2012) Relationship between wood color parameters measured by the CIELab System and extractive and phenol content in *Acacia mangium* and *Vochysia guatemalensis* from fastgrowth plantations. Molecules 17:3639–3652. https://doi.org/10.3390/ molecules17043639
- Makoto K (2021) Juglans-colour, Dryad, Dataset. https://doi.org/10.5061/ dryad.3bk3j9kjr.
- Kabrick JM, Goyne KW, Fan Z, Meinert D (2011) Landscape determinants of exchangeable calcium and magnesium in Ozark highland forest soils. Soil Sci Soc Am J 75:164–180. https://doi.org/10.2136/sssaj2009.0382

Publisher's Note

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Submit your manuscript to a SpringerOpen journal and benefit from:

- ► Convenient online submission
- ► Rigorous peer review
- ▶ Open access: articles freely available online
- ► High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ▶ springeropen.com